

ARTICLE

Open Access

A versatile interferometric technique for probing the thermophysical properties of complex fluids

Gopal Verma¹✉, Gyanendra Yadav², Chaudry Sajed Saraj¹, Longnan Li^{1,3}, Nenad Miljkovic^{3,4,5,6} , Jean Pierre Delville⁷ and Wei Li¹ ✉

Abstract

Laser-induced thermocapillary deformation of liquid surfaces has emerged as a promising tool to precisely characterize the thermophysical properties of pure fluids. However, challenges arise for nanofluid (NF) and soft biofluid systems where the direct interaction of the laser generates an intriguing interplay between heating, momentum, and scattering forces which can even damage soft biofluids. Here, we report a versatile, pump-probe-based, rapid, and non-contact interferometric technique that resolves interface dynamics of complex fluids with the precision of ~ 1 nm in thick-film and 150 pm in thin-film regimes below the thermal limit without the use of lock-in or modulated beams. We characterize the thermophysical properties of complex NF in three exclusively different types of configurations. First, when the NF is heated from the bottom through an opaque substrate, we demonstrate that our methodology permits the measurement of thermophysical properties (viscosity, surface tension, and diffusivity) of complex NF and biofluids. Second, in a top illumination configuration, we show a precise characterization of NF by quantitatively isolating the competing forces, taking advantage of the different time scales of these forces. Third, we show the measurement of NF confined in a metal cavity, in which the transient thermoelastic deformation of the metal surface provides the properties of the NF as well as thermo-mechanical properties of the metal. Our results reveal how the dissipative nature of the heatwave allows us to investigate thick-film dynamics in the thin-film regime, thereby suggesting a general approach for precision measurements of complex NFs, biofluids, and optofluidic devices.

Introduction

Nanofluids have emerged as promising heat transport fluids with enhanced thermal conductivity in a wide range of technological applications. Nanofluids are formed by suspending metallic or nonmetallic nanoparticles in a base fluid^{1–4}. Nanofluids have opened a new dimension in the enhancement of heat transfer technology merely by adding $<1\%$ nanoparticle mass or volume fraction to the base fluids^{1–4}. Since the first study published in 1995¹, NFs have attracted different applications such as coolants in automobile transmission systems, electronic cooling

applications, solar water heating devices, nuclear reactors, radiators, low-cost spectrally selective optical filters, etc.^{4–14}. In these applications, the thermophysical properties of the nanofluid, including its heat transfer characteristics (thermal conductivity, heat capacity) and hydrodynamic properties (surface tension, viscosity), play critical roles in performance^{5,15}. Therefore, the precise characterization of surface and bulk thermophysical properties of a nanofluid is indispensable in ensuring enhanced performance and predictive capability.

Various techniques have been used to explore the thermophysical properties of NFs made from nanoparticles having different shapes, sizes, the mass/volume fractions both form a theoretical and experimental approach. These include transient hot wire, temperature oscillation, and ω methods^{4–19}. Among all developed methods, laser-driven thermocapillary deformation is the most promising

Correspondence: Gopal Verma (gopal@ciomp.ac.cn) or Wei Li (weili1@ciomp.ac.cn)

¹GPL Photonics Lab, State Key Laboratory of Applied Optics, Changchun Institute of Optics, Fine Mechanics and Physics, Chinese Academy of Sciences, 130033 Changchun, China

²School of Physical Sciences, University of Liverpool, Liverpool L69 3BX, UK
Full list of author information is available at the end of the article

© The Author(s) 2022



Open Access This article is licensed under a Creative Commons Attribution 4.0 International License, which permits use, sharing, adaptation, distribution and reproduction in any medium or format, as long as you give appropriate credit to the original author(s) and the source, provide a link to the Creative Commons license, and indicate if changes were made. The images or other third party material in this article are included in the article's Creative Commons license, unless indicated otherwise in a credit line to the material. If material is not included in the article's Creative Commons license and your intended use is not permitted by statutory regulation or exceeds the permitted use, you will need to obtain permission directly from the copyright holder. To view a copy of this license, visit <http://creativecommons.org/licenses/by/4.0/>.

approach to characterize the thermophysical properties of liquids due to its noninvasive, fast, and sensitive features. Thermocapillary deformation induced from localized laser heating and its delayed thermal response have been used to measure the thermal diffusivity and monitor the organic impurities in water^{20–25}. However, due to its direct laser-fluid interaction, thermocapillary deformation has two outstanding challenges which limit its practical application. The first is the fact that it only works for pure fluids. When implemented for nanofluids and biofluids, a complex interplay of radiation, thermocapillarity, and scattering forces form which can lead to inaccurate determination of thermophysical properties. The second challenge is that thermocapillary deformation does not work for applications where the pump laser can lead to damage of the fluid. These include soft biological fluids²⁶ or systems where the fluid is confined in a closed surface, such as heat pipes.

In this article, we address these two challenges by proposing a versatile optical technique based on pump-probe interferometry^{27–30} to characterize the thermophysical properties of both NFs and biological fluids. We show three exclusively different pump laser-induced heating configurations and demonstrate their wide applicability. Peculiarly, (1) for fluids that cannot be illuminated with the pump laser directly from the top such as biological fluids or NFs, we show that a bottom illumination configuration enables the characterization of the precise thermophysical properties. (2) For applications scenarios where bottom illumination is prohibited, and top illumination is required, such as the characterization of liquids on thick substrates like skin, we demonstrate the precise characterization of NFs by quantitatively isolating the competing effects of all three forces by taking advantage of their different time scales. (3) We show the direct measurement of NF thermophysical properties inside a closed cavity for applications mimicking heat pipes where the fluid cannot be exposed to light or the ambient environment. The measured results from our various configurations characterize the thermophysical quantities without introducing the competing effects of radiation pressure and scattering forces. These results are self-consistent and in good agreement with existing techniques. Our technique works for nearly all liquids and can be applied to a wide range of application scenarios for precise in-situ characterization of the thermophysical properties of complex fluids.

Direct laser interactions with complex NF

The schematic diagram shown in Fig. 1a represents the fundamental processes that are established during direct laser interaction with a complex NF. These include optical momentum-induced deformation^{27,28}, scattering with nanoparticles^{31,32} in the fluid, heating-induced deformation^{33–35}, as well as potential damage that may be induced

by the laser, especially for soft biofluids. The surface deformation at the interface occurs as a result of these competing processes. The complex interplay of these processes makes it challenging to investigate the transient surface deformation for precise thermophysical characterization of NFs. Here, we address these challenges and demonstrate the characterization of a NF using three exclusively different types of pump laser-induced heating configurations as shown in Fig. 1b. Below we discuss each configuration and demonstrate their wide applicability.


Results

Pump laser illumination from the bottom of the substrate

For our first approach, we introduce a configuration where the pump laser is illuminated from the bottom of the substrate. Instead of direct laser liquid interaction, this configuration allows us to precisely characterize the thermophysical properties of complex NFs and biological fluids by eliminating scattering and radiation pressure effects. It also isolates the potential damage from the pump laser for applications when characterizing biological fluids is required²⁶.

In the bottom illumination setup (Fig. 2), we used a solid-state green laser. This laser serves as a heating beam for the generation of thermocapillary convection in the nanofluid by substrate heating. The power of the heating beam was varied depending on experimental requirements. The probe laser beam (He–Ne laser, $\lambda = 632$ nm, beam waist 1 mm) was focused on the liquid surface with a lens (focal length 200 mm) to form a Newton Ring type interference with the fringe pattern reported in refs. ^{20,27–30}. The focused probe beam has a beam waist of 110 μm (see Supplementary Fig. S1). The experimental procedure includes the following steps: a water-based nanofluid made from Al_2O_3 or a hybrid NF ($\text{Al}_2\text{O}_3 + \text{Graphene-oxide (GO)}$ nanosheet) having an initial volume fraction ($\phi = 0.05\%$) is placed on a Copper (Cu) substrate having a large radius of curvature (see “Materials and methods”). The thickness of the nanofluid layer (h_0) was chosen to exclude the influence of thermogravitational convection in the process of thermocapillary deformation, h_c ²³. We used a transparent glass enclosure to reduce the evaporation rate of the NF so that the concentration variation of the NF during measurement is minimized.

The evaporation of NF produced oscillations in $I(t)$ (blue curve in Fig. 2b) which served as a reference to determine the direction (dimple/bump) of the deformation^{20,27–30}. The static evaporation rate also enabled us to have different concentrations of NF for our experiment. Tracking the central intensity of the fringe $I(t)$ allowed self-calibrating time-resolved measurement of optical thickness variation. One fringe collapse resulted in $(I_{\text{max}} - I_{\text{min}}) \equiv \lambda/4n$ (for $\lambda = 632$ nm,

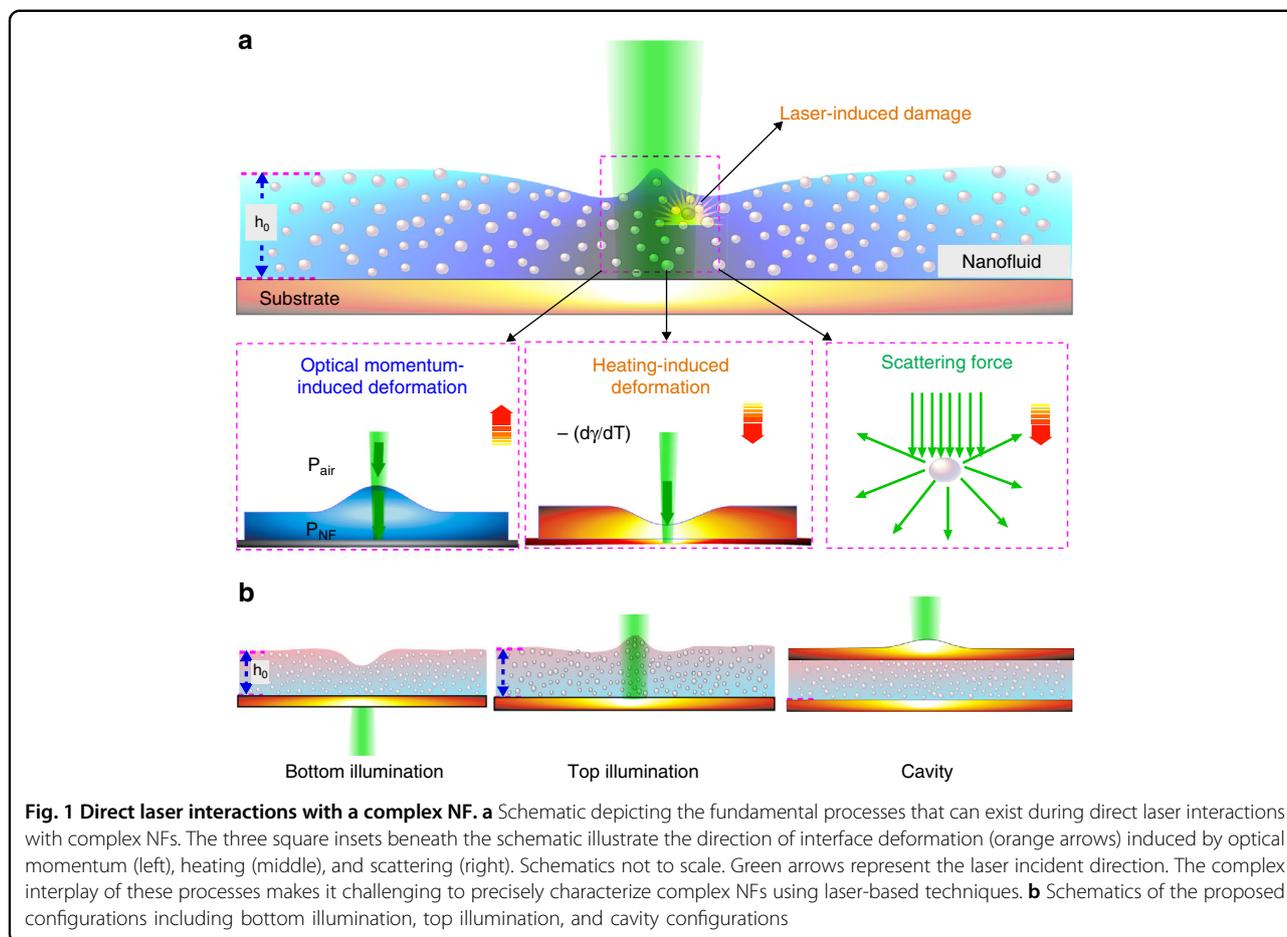

$n = 1.33$) = 118 nm change in the optical path length in the NF drop. By further resolving the intensity levels between the maxima and the minima, we achieved remarkable precision of ~ 5 nm. We have also shown the connection of the intensity signal in the center of the photodetector with the complex temporal and radial dependence of the laser-induced surface deformation in the fluid (Eqs. S1, S2), and probe beam waist dependent phase shift and in corresponding thermophysical properties change (Supplementary Figs. S2, S3).

The base fluid, nanomaterials, and human saliva initial properties are listed in Table 1, which have been obtained from refs. 36–38.

When a Gaussian laser beam is incident to an absorbing Cu substrate covered with a transparent NF droplet, a nonuniform temperature distribution $\Delta T(r, t, z)$ is produced at the solid-NF interface^{33–35}. The heat from this source distributes both into the depth of the substrate and the bulk of the NF layer. As a result, the isotherm will reach the free surface of the NF after a lag time^{21,23} of $\tau_d = h_0^2/4D_f$, where $D_f = k/\rho c_p$ denotes the thermal diffusivity of the fluid medium having thermal conductivity k and specific heat c_p .

For small $\Delta T(r, t, z)$, all thermal properties are assumed to be constant except surface tension. The interface deformation h is allowed to vary linearly (Eq. S3) with the liquid temperature^{20,33}. Temperature variation of the free liquid surface leads to a local decrease in surface tension, $\gamma = \gamma_0 + \gamma_T(T - T_0)$ where, γ_0 is the surface tension of the liquid at a reference temperature T_0 , and $\gamma_T = d\gamma/dT$ is the surface tension coefficient, which is negative for the majority of pure liquids^{21,23}. Consequently, a radially outward surface tension gradient forms along the free liquid surface, $\partial\gamma/\partial r = \gamma_T(\partial T/\partial r) > 0$ that triggers tangential thermocapillary stress along the interface directed toward the regions of highest surface tension. This force is balanced by the velocity gradient (viscous stress) in the bulk layer. This process induces a radially outward thermocapillary flow, which leads to a beam-centered dimple on top of the NF droplet interface²⁰. For most fluids, including Al_2O_3 -NF, $\gamma(T)$ decreases with higher T ($\gamma_T > 0$) which leads to a thermocapillary dip^{33,34}. To measure the transient height of the thermocapillary dimple $h(t)$, we detected local interference intensity $I(t)$ of the central fringe with a photodiode (PD) and a 2 mm aperture opening as shown in Fig. 2a.

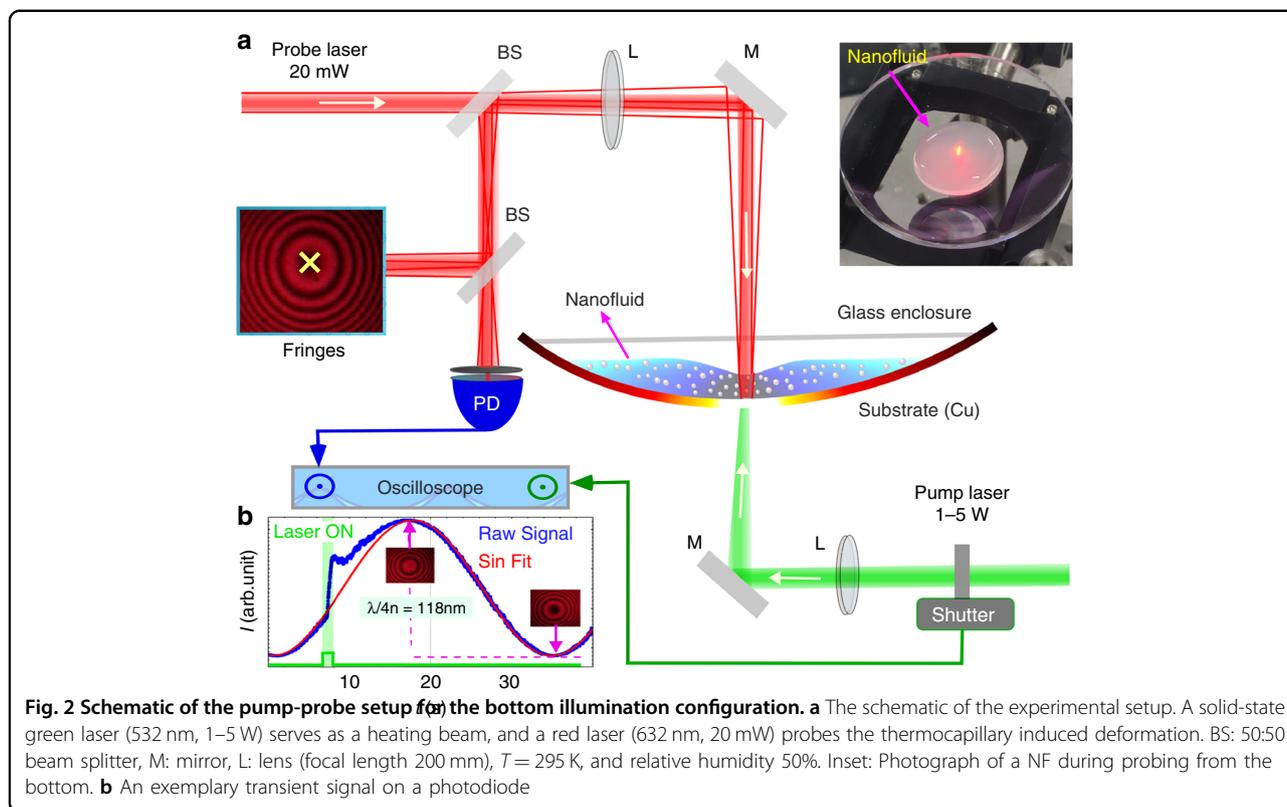



Table 1 Base fluid, nanomaterials, and human saliva properties at $T = 295$ K

Parameters	Water	Al ₂ O ₃	GO	Saliva
ρ (kg m ⁻³)	997	3987	1800	1002
k (W m ⁻¹ K ⁻¹)	0.6	40	3000	0.58
c_p (J kg ⁻¹ K ⁻¹)	4180	773	790	3760
η (mPa S)	0.89	—	—	1.12

Just after switching on the pump laser beam, the probe signal did not change for a certain time interval, herein referred to as the thermocapillary delay time τ_d of the response. The maximum deformation $h(r=0)$ rapidly increases in time after the delay time τ_d and approaches steady state thereafter. Note that the time to reach the temperature isotherm at the Cu–NF interface for a Cu substrate thickness $h_{Cu} = 300 \mu\text{m}$ is $\tau_{Cu} = h_{Cu}^2/4D_{Cu} = 9$ ms which is very small compared to $\tau_{th} = 0.82$ ms = 160 ms. We demonstrate three different concentrations of NF particle volume fractions of $\phi = 0.1, 0.3,$ and 0.5% in water to show the experimental signal in Fig. 3a. We found that for the same experimental parameters (laser power and beam waist), the deformation height for $\phi = 0.1, 0.3,$ and 0.5% with water to have a decreasing order because $\gamma(T)$ decreases with an increase in ϕ .

The transient signal in Fig. 3a gives the τ_d and time constant for the thermocapillary deformation τ_{th} which are related to the diffusivity and viscosity of the NF (as shown in Fig. 3b) and water using the relation $\tau = h_0^2/(4D_f)$ and $\tau_{th} = 3\eta w_{th}^4/(\gamma h_0^3)$. For example, water gives $\tau_{th} = 0.82$ s. This is very large for a thick sample ($h_0 = 300 \mu\text{m}$). We expect this such behavior as heating is a dissipative process; hence the thermal spot size increases at the liquid surface. Therefore, the dynamics of the interface deformation induced by heating starts to belong to the thin-film regime, which has a time scale²⁰ of $\tau_{th} = 3\eta w_{th}^4/\gamma h_0^3$. Since we know other parameters in τ_{th} we found $w_{th} = 4.8$ mm. Hence, $h_0 w_{th} \ll 1$ is satisfied.

Figure 3c shows $\Delta T(r, t, z)$ and its time derivative at the air–NF interface. The peak in the plot indicates that the present temperature gradient has become sufficiently large enough to initiate observable surface deformation at the NF–air interface. This peak also enables us to calculate the value of τ_d . To obtain τ_d with higher precision, we plot the semi-log of this curve (inset of Fig. 3c), where the maxima verified our approach for this calculation. In Fig. 3d, one could easily notice that the thermal spot size at the Cu substrate and NF–air interface are different as it is broadened at the air–water interface (also at the air–NF interface, not shown) due to the diffusive nature of heat. This peculiar nature of thermal spot width variation allowed us to investigate the thick NF sample under a

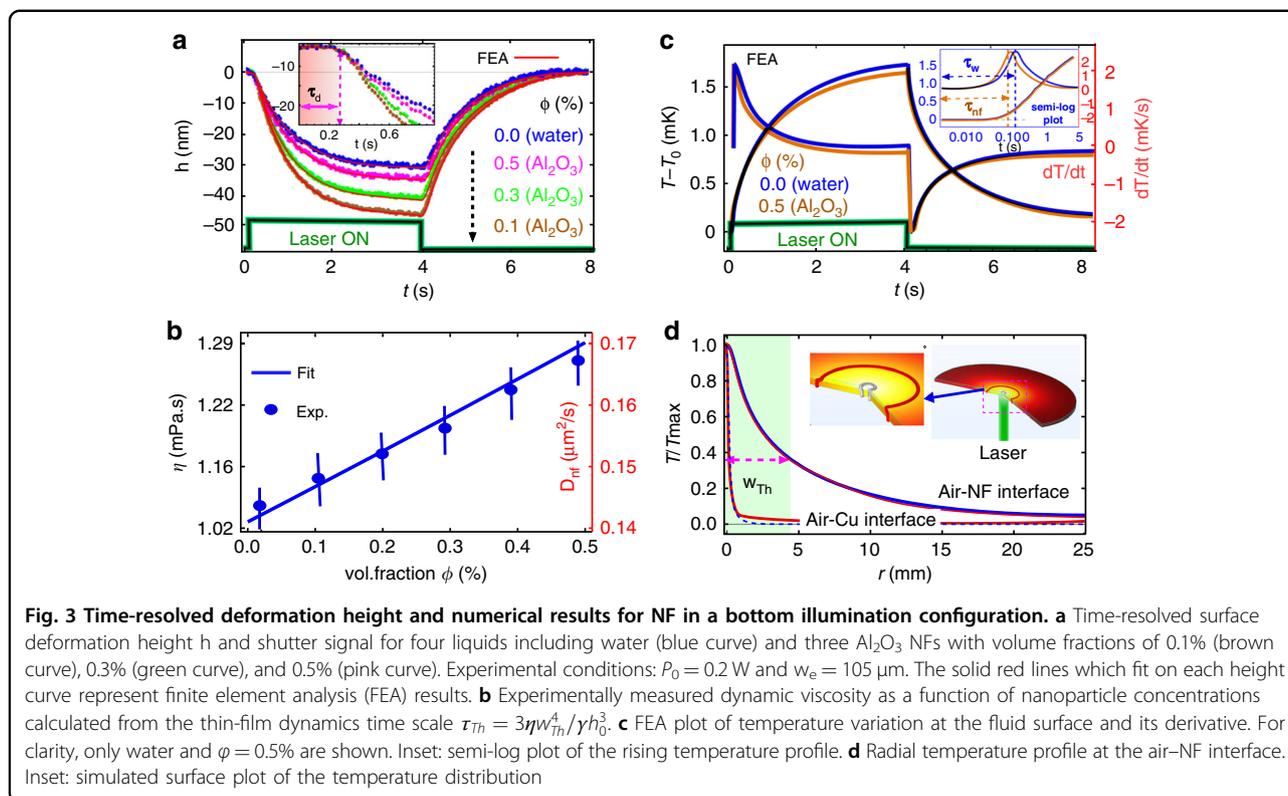


thin-film regime and provides reliability in our calculation of thermophysical quantities. To validate our experimental results, we performed a numerical simulation using COMSOL Multiphysics (see “Materials and methods”). We used the data from Table 1 for the base fluid, different nanoparticles, and saliva as a reference for calculating the physical properties of the NF and saliva using the mixture model³⁹.

Hybrid-nanofluids and complex biological fluids (human saliva)

To further demonstrate the wide applicability of our technique, we investigated fluids with more complex components. As a proof-of-concept demonstration, we choose a hybrid NF and a bio-fluid (human saliva) as two examples and investigated their thermophysical properties.

A hybrid nanofluid is a solid-liquid mixture formed by dispersing two or more different nanoparticles suspended in a liquid, which displays enhanced thermophysical properties and rheological characteristics compared to nanofluids made from a single nanoparticle component^{40–42}. We prepared an aqueous Al_2O_3 and graphene-oxide (GO) nanosheet hybrid NF for the characterization of thermal properties. Figure 4a presents the time-resolved deformation height and numerical results for the hybrid NF and human saliva samples. Figure 4b shows the influence of the NP

volume fraction on the dynamic viscosity and thermal diffusivity of the hybrid NF, which is extracted from Fig. 4a. The results indicate that both properties of the hybrid NF increase with increased NP volume fraction in the range from 0 to 0.5%. The results show that the nanoparticle volume fraction had a significant influence on the hybrid nanofluid thermophysical properties because the thermal conductivity of GO and Al_2O_3 nanoparticles are larger than that of deionized water as well as the Al_2O_3 NF. The nanoscale sensitivity of our noninvasive optical technique to surface deformation measurement allowed us to characterize the complex biological fluid (human saliva) in a similar non-contact manner without damaging it. An absence of damage is ensured due to the micro-Kelvin scale temperature rise required to achieve a few nanometers deformation of the sample surface. Figure 4c, d shows that the transient signal of the deformed surface and extracted viscosity and diffusivity of fresh human saliva are consistent with previously reported values³⁸. It is noticeable that the thermal diffusivity of saliva decreases as water content decreases. Human saliva was collected from a healthy donor, aged 25–35 years, between 9:00 and 11:00 AM. The donor refrained from eating or drinking for 2 h prior to collection. Human saliva is comprised of 99.5% water and contains many essential substances, including electrolytes, mucus, antibacterial compounds, and

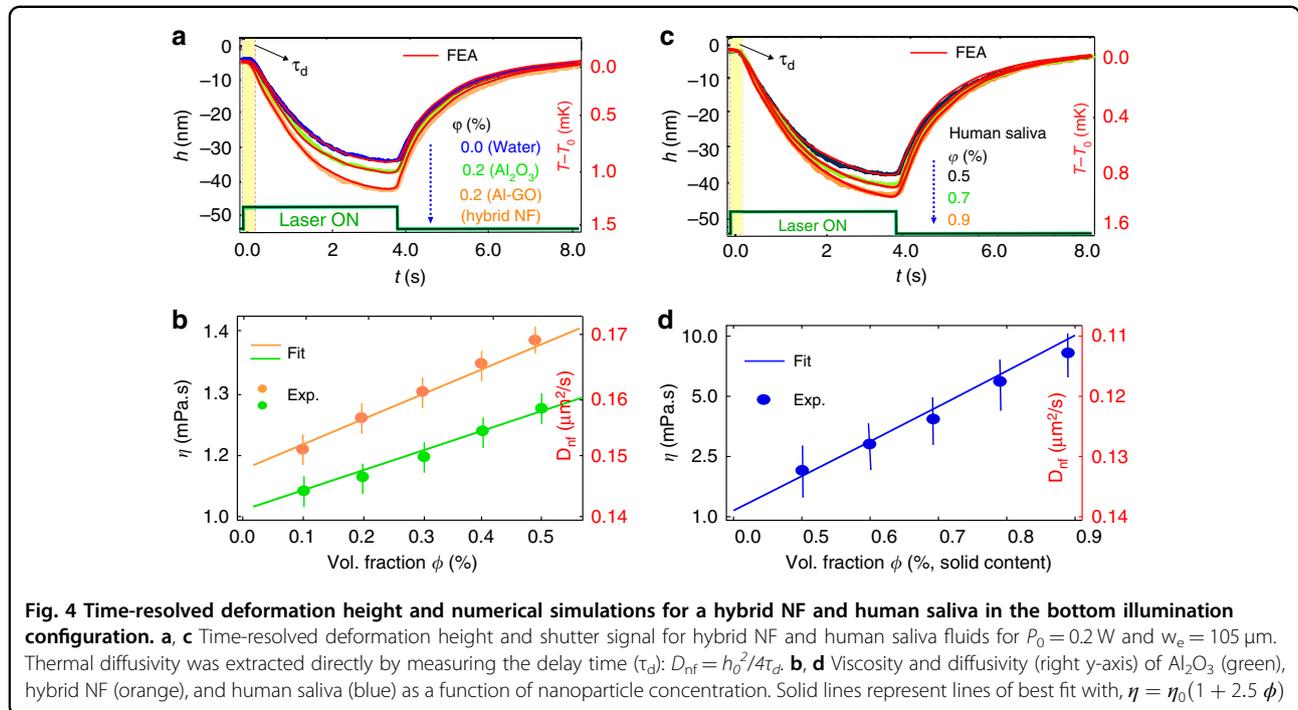

various enzymes. Hence for our volume concentration of saliva calculation, we considered the solid content as spherical particles of mean radius (r_0).


Top pump laser illumination on the NF surface

We now present our second configuration using top pump laser illumination. This configuration can be used in application scenarios where bottom illumination with the laser is not easily accessible (e.g., semi-infinite substrate, structured surfaces like cloths, skin, etc...). Unlike previous work^{20–25} where the complex interplay of radiation, thermocapillarity, and scattering forces were not considered, here we show that we can precisely characterize NFs by quantitatively isolating the competing effects of all three forces by taking advantage of their different time scales. For optically transparent fluids (water) and substrates that do not absorb light at the pump laser wavelength, thermal effects are negligible on the water surface. Light momentum discontinuity results in a radiation pressure $\Pi_0 = \frac{2}{c} \left(\frac{n-1}{n+1} \right) I_0$, where $I_0 = 2P_0/\pi w_e^2$. The radiation pressure produces a transient nanoscale bulge having a time scale^{20,29,32} $\tau_r = 2\eta w_e/\gamma$ and an attained stationary height, $h_m(r) = \frac{P_0(n-1)}{\pi c(n+1)} \int_0^\infty \frac{k J_0(kr) e^{-w_e^2 k^2/8}}{y k^2 + \rho g} dk$ where, J_0 is the zeroth-order Bessel function^{20,28}. For dilute Al_2O_3 NF and biofluids, the absorption coefficient (A_e) is higher than that of water. Therefore, in this case, due to weak heating, we observed a complex interplay between three forces (Fig. 5a)

comprised of thermocapillary stress, radiation pressure, and volumetric force due to light scattered f_{scatt} by the nanoparticles^{31,32}. In the case of spherical particles of radius r_0 such that $r_0 \ll \lambda$, the order of magnitude of the scattering force density involved in our experiments is inferred from the relationship $f^{scatt} \approx \tau n/c$ ^{31,32}.

The turbidity (τ) of the NF has been found to be of the order of 50–100 m^{-1} . Notice that $\tau \gg \alpha_{Ab}$, confirming that the light-induced force density originates mainly from light scattering. Using $n = 1.33$ as a characteristic value for the refractive index and $I_0 = 2P_0/\pi w_e^2$ with $P_0 = 0.1 - 1$ W, we obtained $f^{scatt} \approx 1 \times 10^2 - 2 \times 10^3 \text{ N m}^{-3}$. This force density is exerted along the direction of propagation i.e perpendicular to the NF surface, and its competing effect is shown in Fig. 5b, c. We implemented the f^{scatt} as a volumetric force in Eq. (2) (see “Materials and methods”) and radiation pressure and heating-induced surface stress at the air–water/NF interface as a boundary condition.

Radiation pressure-induced fluid deformation has a fast time scale ($\tau_r = 2\eta w_e/\gamma$) as one can see in Fig. 5b, c. The other two forces are related to the bulk flow of liquid. Therefore, radiation pressure fluid deformation appears on a different time scale and becomes distinguishable after some time of laser exposure. Figure 5b shows this expected long-term dynamics of interface deformation. Differences in time scales are even more noticeable when the pump laser is turned off. At first, the interface relaxes rapidly. Radiation pressure induces a bulge following the pump beam with steps near the rising/falling edges, as

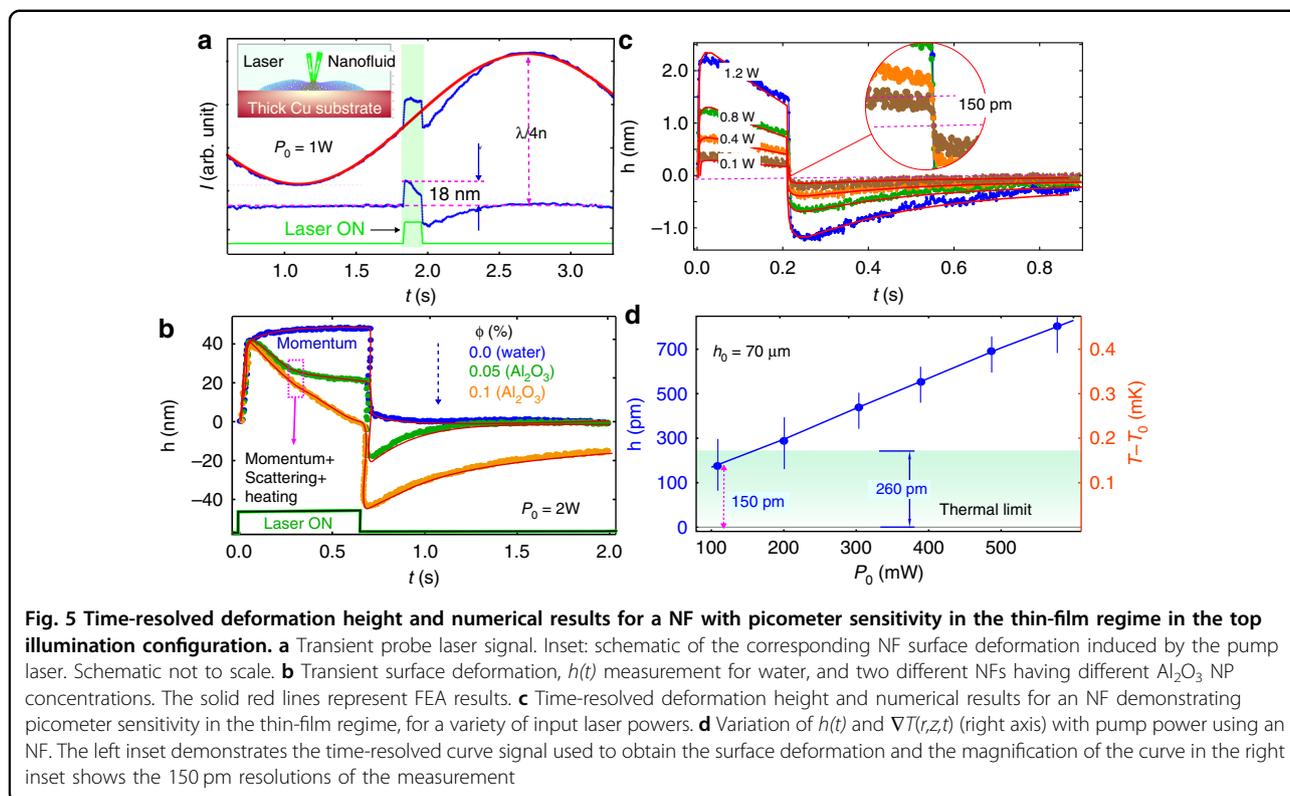


previously observed in transparent fluids^{20,28,30}. Thermocapillary and scattering force-induced dimple formation exhibited slow dynamics, which were isolated as shown in Fig. 5b. The scattering force depends on the direction of incident laser light. Hence it could induce a bulge (as the radiation pressure case) on the NF surface when we shine a laser from the bottom of the glass substrate. We also performed an experiment in a thin-film NF sample for sample height (h_0) about $70\ \mu\text{m}$ and $\phi = 0.05$, which allowed us to measure picometer-scale sensitivity of the NF surface deformation. Figure 5c shows the power-dependent transient probe signal which linearly depends on laser power as shown in Fig. 5d. The precision in surface deformation measurement is restricted due to the thermal limit, which is associated with the NF's interfacial fluctuations and given by $\sqrt{k_B T / \gamma}$, where k_B is the Boltzmann's constant. The value for this system is $\sim h = 260\ \text{pm}$. Noticeably, we have measured the deformation height of $\sim 150\ \text{pm}$, which is beyond the thermal limit. This displacement is measured without any lock-in or modulation on contrary to ref. ³³ as for thin films, viscous forces dominate and suppress other fluctuations. These different degrees of precision in thick and thin films of the sample are due to bottom frictions of the substrate and gravity–capillary waves. For thick films, bottom friction vanishes and gravity–capillary waves are not damped by viscous dissipation²⁰ allowing us approximately a 1 nm

precision in deformation height measurement. However, bottom substrate friction becomes dominant in the thin-film regime, and gravity–capillary waves are damped by viscous dissipation, allowing us to reach picometer-scale precision.

Nanofluid characterization inside a metallic cavity

We now introduce our third configuration where we show that the nanofluid inside a metallic cavity can be characterized using our approach. This configuration has its unique advantages in applications where the fluid is confined within a closed surface³⁵ such as for a heat pipe, or where a fluid cannot be exposed to light or to the ambient environment. This is particularly important for applications where volatile organic compounds are present and can be absorbed by the working fluid^{43–47}. It has been shown that the effect of surface heat transfer from the sample to the surroundings could be meaningful in the determination of physical parameters by laser-excited photothermal lens spectroscopy⁴⁸. Here, we extracted the thermophysical properties of a NF by measuring the thermoelastic response of the laser-heated metal (Cu) cavity. The nanometric sensitivity of our technique allowed us to measure the laser heating-induced thermoelastic deformation (see “Materials and methods”). Figure 6a shows the schematic of the setup and surface thermoelastic response of a metal cavity filled with air,

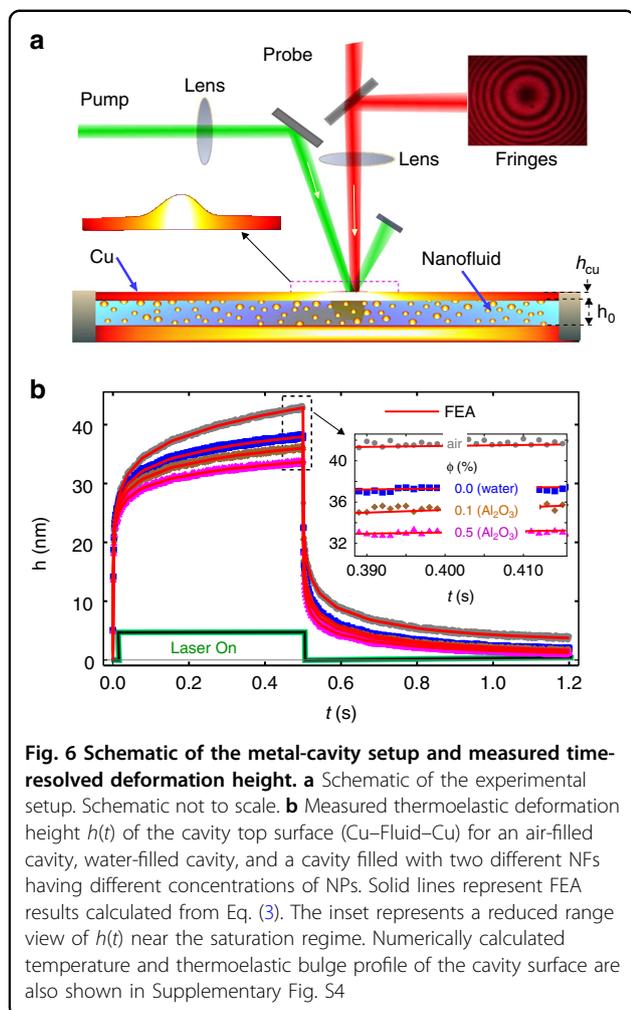

water, and two different concentrations of NFs. We observed (Fig. 6b) that the thermoelastic deformations in the cavity are higher when there is air when compared to water or NF. This is because of the increasingly higher thermal conductivity when water or NF is introduced as a fluid, compared to air. Our results could be used to obtain the physical properties of fluids having low optical absorption by using a reference solid sample in both thermal lens and thermal mirror experiments. This configuration could be useful for the noninvasive measurement of blood or any other fluid inside the viscoelastic material tube (e.g., nylon, vein/artery). Because the flow of blood or external stresses produce pressure on the vessel wall, wall deformation may occur³. The thermal, optical, and mechanical properties of the cavity listed below (Table 2) associated with characteristics values found from experimental data (shaded gray) and ref.⁴⁸ are used for the numerical simulations.

We now discuss the self-consistency and robustness of our technique. Table 3 summarizes the measured viscosity and surface tension coefficient of a NF, hybrid NF,

Table 2 Additional physical parameters obtained from the experimental data of Figs. 3 and 4

Parameters	Water	Al ₂ O ₃	Al ₂ O ₃ + GO	Saliva
τ_d (ms)	156	154, 148, 144	145, 143, 140	140, 155, 160
$-\frac{d\sigma}{dT}$ (10^{-3} N m ⁻¹ K ⁻¹)	0.18	0.28, 0.26, 0.23	0.16, 0.15, 0.13	0.18, 0.17, 0.16

human saliva, and compares them with literature values. Good agreements are found for all fluids. It is also noteworthy to mention that the measured quantities under all heating configurations are consistent (see Supplementary Table S1). For example, the measured viscosity of Al₂O₃ NF (with $\phi = 0.1$) in the bottom (Fig. 3a), top (Fig. 5a), and cavity (Fig. 6b) configurations are 1.14, 1.12, and 1.15 mPa s, respectively. The measured results are consistent and very close to the theoretical value of 1.13 mPa s. Furthermore, the measured quantities are independent of apparatus parameters such as substrate thickness and laser spot size, depicting the robustness of our technique.


Discussion

Four prime capabilities of our technique prove its versatility in measuring thermophysical and mechanical properties of fluids. The first capability is the nanometric sensitivity (picometer for thin-film) and self-calibrating nature of the technique. This capability allowed us to measure the time-resolved thermophysical properties of NFs, biological fluids in various configurations. The delayed thermocapillary signal directly gives the physical properties (NF and saliva) for the substrate used. An important consequence of heating the substrate from the bottom and NF inside the metal cavity is that it works for nearly all kinds of liquid as it eliminates the effects of scattering and radiation forces, as well as the potential damage induced by the laser. In addition, measuring the surface deformation beyond the thermal limit without the use of any electrical modulation distinguishes our work from past approaches. The second capability is the ability to measure weakly absorbing NFs thermal properties for a thick substrate by isolating the competing effects of thermal, scattering, and momentum transfer. The fluid dynamics can be obtained by analyzing different time scales in the surface deformation signal. This analysis can also be applicable to structured surfaces, e.g., skin, cloth, where it is difficult to shine laser from the bottom for heating²⁹. The third capability is that the transient thermoelastic signal is very useful for NFs in confined environments, where heat coupling between the solid and NF provides thermophysical properties of the nanofluid only if a solid reference sample is used. The fourth capability is

Table 3 Measured dynamic viscosity and surface tension coefficient of a NF (gray shaded rows) and literature reported values for Al_2O_3 (ref. ³⁶), $\text{Al}_2\text{O}_3 + \text{GO}$ (ref. ³⁷), and saliva (ref. ³⁸)

Parameter	Water	Al_2O_3 ($\phi = 0.1, 0.3, \text{ and } 0.5$)	$\text{Al}_2\text{O}_3 + \text{GO}$ ($\phi = 0.1, 0.3, \text{ and } 0.5$)	Saliva ($\phi = 0.5, 0.7, \text{ and } 0.9$)
η (mPa s)	1.03	1.14, 1.19, 1.27	1.18, 1.25, 1.38	1.74, 3.48, 9.20
	0.95	1.13, 1.17, 1.26	1.17, 1.27, 1.39	1.75, 3.40, 9.10
$-\frac{d\sigma}{dT}$ ($10^{-3} \text{N m}^{-1} \text{K}^{-1}$)	0.18	0.28, 0.26, 0.23	0.16, 0.15, 0.13	0.17, 0.15, 0.11
	0.19	0.29, 0.27, 0.21	0.17, 0.16, 0.12	0.18, 0.16, 0.13

The error bar is shown in Fig. 3

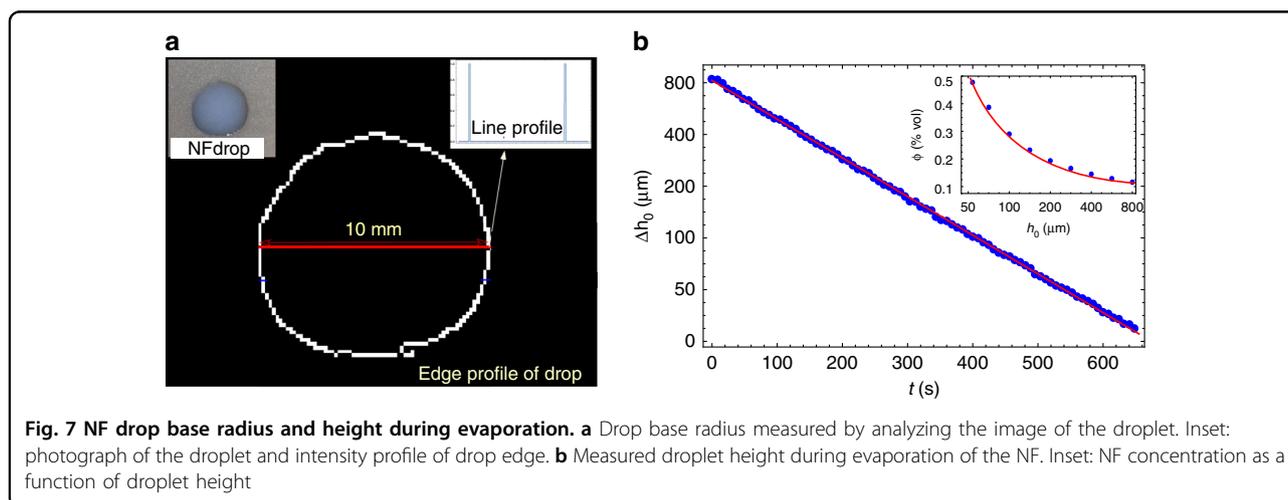

the noninvasive nature of the technique which is crucial for investigating the properties of complex hybrid-NFs and biological fluids^{26,40}. We have demonstrated the measurement of thermophysical properties of human saliva by merely changing the temperature of the sample by a few μK and in a single measurement. Apart from this, our approach is also applicable for high concentration NFs where non-Newtonian behavior (viscoelastic) is expected^{20,40,49–51}. Nanofluid films having thicknesses of a few nanometers inside the cavity would be interesting because the change in Brownian motion of the nanoparticles would play an important role in enhancing the thermal conductivity¹⁹.

In conclusion, our results open the possibility of applying an interferometric method for the measurement of thermophysical properties of NFs, hybrid-NFs, and biological fluids in three different types of pump laser-induced heating configurations. Future work is needed to extend the precision of our technique below 100 pm by using a twisted light beam as the probe beam⁵², that can be used to detect femto-Newton-range forces with sensitivity close to the thermal limit⁵³. It would also be helpful in laser-induced cooling of solids⁵⁴ to find the bump on NF/complex fluid surface. Our results and method have the potential to make notable contributions

to opto-rheology²⁰, thin-film nanometrology⁵⁵, and designing tailored optical propulsion forces for controlled transport of resonant optical-force-guided microfluidics⁵⁶.

Materials and methods

Nanofluid preparation

The average diameter of Al_2O_3 nanoparticles (provided by Nachen, Beijing, China) is 40 nm. Morphologies of these particles are basically spherical or near-spherical. Al_2O_3 –water nanofluids with 0.01 vol.% ~0.5 vol.% were produced by a two-step method without any surfactant. Ultrasonic vibration with an ultrasound generator (20 kHz, 100 W) was used to disperse Al_2O_3 nanoparticles in DI water for 3 h. Figure 7 shows photographs of Al_2O_3 –water.

We quantified the concentration of the evaporating NF during experiments by measuring the drop height as shown in Fig. 7.

Finite element analysis (FEA)

We performed numerical simulations with realistic sample dimensions to validate the experimental data and temperature change corresponding to deformation height. The system is symmetric around the z axis (incident laser beam axis). Hence, the 3D problem can be reduced to a 2D axisymmetric geometry. Two main physical mechanisms

involved in the generation of thermocapillary convective flow are: heat transfer modeled by the heat equation and fluid dynamics modeled by the Navier–Stokes equation, both linked by the stress equilibrium condition $\partial\gamma/\partial r = \gamma_T(\partial T/\partial r)$. The two-phase mixture model has been extensively used for two-phase flows where the phases move at different velocities and are strongly coupled. The mixture model solves the continuity, momentum, and energy equations for the nanoparticles–fluid mixture. The momentum equation of the nanofluid is the total of the momentum equations for the fluid and nanoparticles phases. The equation of volume fraction is the continuity equation of the nanoparticle phase³⁹. Thermal properties of nanofluids³⁹: NF density: $\rho_{nf} = \varphi\rho_n + (1 - \varphi)\rho_f$, NF-specific heat: $(\rho C_p)_{nf} = \varphi(\rho C_p)_n + (1 - \varphi)(\rho C_p)_f$, NF viscosity: $\mu_{nf} = \mu_f/(1 - \varphi)^{2.5}$ and effective thermal conductivity used for input parameters for numerical simulation are defined as:

$$\frac{k_{nf}}{k_f} = \frac{1 - \varphi + 2\varphi \frac{k_n}{k_n - k_f} \ln\left(\frac{k_n + k_f}{2k_f}\right)}{1 - \varphi + 2\varphi \frac{k_f}{k_n - k_f} \ln\left(\frac{k_n + k_f}{2k_f}\right)} \quad (1)$$

Temperature fields

We used the Heat Transfer in Solid Fluids module to find temperature rise distribution within the sample and substrate. This is given by the solution of the coupled heat conduction differential equation³⁴, $\partial_t T_i(r, z, t) - D_i \nabla^2 T_i(r, z, t) = q_i q(r, z)$ with proper boundary and initial conditions as given in ref. ³⁴. Where $D_i = k_i/\rho_i c_{pi}$ is the thermal diffusivity, k_i is the thermal conductivity, ρ_i is the mass density, and c_{pi} is the specific heat for the solid substrate ($i = s$) and fluid ($i = f$). The laser as a heat source is defined as $q_s = 2P(1 - R)\phi_{th}/\pi c_s \rho_s w_e^2$ and $q(r, z) = \exp\left(\frac{-2r^2}{w_e(z)^2}\right) \exp(-A_b z)$. Since the fluid is assumed to be non-absorbing, $q_f = 0$. The portion of the absorbed power converted into heat is represented by ϕ_{th} , which in this case is ≈ 1 . We used boundary heat source in COMSOL as a boundary condition, where P_0 is the excitation power, R is the sample surface reflectivity. The heat flux or losses from boundaries is specified by $Q_z = -\vec{n} \cdot \nabla T = h_N(T - T_\infty) + \varepsilon \sigma_B(T^4 - T_\infty^4)$ where \vec{n} is the outward-oriented unit normal vector. h_N is the convective heat transfer coefficient of the substrate, σ_B is the Stefan–Boltzmann constant, ε is the emissivity of the substrate.

Thermocapillary deformation

The Laminar Two-Phase Flow, Moving Mesh module was used to solve the Navier–Stokes equation for

incompressible flow.

$$\rho \frac{\partial v}{\partial t} + \rho(v \cdot \nabla)v = -\nabla P + \mu \nabla^2 v + \sum F_v \quad (2)$$

v describes the flow velocity, P is the pressure, ρ is the fluid density, μ is the dynamic viscosity and F_v is the volume force. The ratio between the convective and diffusive mechanisms is given by the thermal Peclet number, which is defined as $Pe_{th} = C_p U L/k$, where L is a characteristic length, the height h_0 of the liquid layer in this case and U is a characteristic velocity. The Peclet number attains a maximum of 100 at the interface near the laser spot and values below 20 elsewhere. In consequence, the convective transfer mechanism is dominant in the system, meaning that the flow velocity field will have a significant effect on the temperature field. The Maximum attained Reynolds number $Re = UL/\mu$ is obtained at the interface near the laser spot with a value of $\approx 10^{-4}$ and values below this elsewhere. This means that the convective transfer mechanism is the dominant one and the flow is considered to be laminar. We used our extracted experimental parameters as input parameters for simulation e.g., viscosity, and surface tension coefficient (see Table 1), and other thermophysical properties (density, heat capacity, and thermal conductivity) of the nanofluid using Table 4 as a function of volume fraction using the relation given in refs. ^{39,50}.

Thermoelastic displacement

The Theory of Elasticity can be used to calculate the surface displacement caused by a laser-induced, nonuniform temperature distribution. In the quasi-static approximation,

Table 4 Base fluid, nanomaterial, and initial substrate properties at room temperature

Parameters	Units	Values
k_s , air, water	(W m ⁻¹ K ⁻¹)	201, 0.026, 0.6
D_s , air, water	(10 ⁻⁶ m ² s ⁻¹)	6.94, 21.9, 0.14
$D_{nf}^{\phi=0.1,0.5}$	(10 ⁻⁶ m ² s ⁻¹)	0.14, 0.17
ρ_s , air, water	(kg m ⁻³)	8960, 1.17, 998
C_s , air, water	(J kg ⁻¹ K ⁻¹)	384, 1005, 4180
R	—	0.52
α_T	(10 ⁻⁶ K ⁻¹)	10.3
v_s	—	0.31
E_s	(10 ⁹ Pa)	120
h_{Cu} (top)	μm	300
h_{Cu} (bottom)	μm	500
h_0 (fluid)	μm	1000

the thermoelastic equation⁴⁸ is given by:

$$(1 - 2\nu)\nabla^2 u(r, z, t) + \nabla[\nabla \cdot u(r, z, t)] = 2(1 + \nu)\alpha_T \nabla T(r, z, t) \quad (3)$$

here, $u(r, z, t)$ is the displacement vector, ν is Poisson's ratio, and α_T is the linear thermal expansion coefficient. We applied a laser heat source as a boundary condition (in Heat Transfer module) at the free surface of a Cu and "Structural Mechanics Module" to solve the above equation for thermoelastic displacement. We applied a no-slip boundary condition at the solid and fluid interface and a fixed boundary condition at the edges. As shown in Fig. 6, the experimental and FEA results are in good agreement. Initially, we experimented air-filled cavity for a given laser power 2 W and $w_e = 105 \mu\text{m}$ in crosscheck the value of Cu properties. Then, we experimented with water and NFs.

Acknowledgements

This work was supported by the National Natural Science Foundation of China (grant nos. 62134009, 62121005), the Innovation Grant of Changchun Institute of Optics, Fine Mechanics and Physics (CIOMP), Jilin Provincial Science and Technology Development Project (grant no. YDZJ202102CXJD002), Bill & Melinda Gates Foundation (INV-009181).

Author details

¹GPL Photonics Lab, State Key Laboratory of Applied Optics, Changchun Institute of Optics, Fine Mechanics and Physics, Chinese Academy of Sciences, 130033 Changchun, China. ²School of Physical Sciences, University of Liverpool, Liverpool L69 3BX, UK. ³Materials Research Laboratory, University of Illinois, Urbana, IL, USA. ⁴Department of Mechanical Science and Engineering, University of Illinois, Urbana, IL, USA. ⁵Department of Electrical and Computer Engineering, University of Illinois, Urbana, IL, USA. ⁶International Institute for Carbon Neutral Energy Research (WPI-I2CNER), Kyushu University, 744 Motoooka, Nishi-ku, Fukuoka 819-0395, Japan. ⁷University of Bordeaux, CNRS, LOMA, UMR 5798, F-33405 Talence, France

Author contributions

G.V., J.P., and W.L. jointly conceived the idea. G.V. and C.S.S. performed the experiments. G.V., G.Y., L.L., N.M., J.D., and W.L. performed simulations and analyses. G.V., N.M., and W.L. wrote the manuscript with input from all authors. W.L. supervised the project.

Data availability

The data that support the findings of this study are available from the corresponding author upon reasonable request.

Conflict of interest

The authors declare no competing interests.

Supplementary information The online version contains supplementary material available at <https://doi.org/10.1038/s41377-022-00796-7>.

Received: 13 February 2022 Revised: 1 April 2022 Accepted: 9 April 2022

Published online: 28 April 2022

References

- Choi, S. U. S. & Eastman, J. A. Enhancing thermal conductivity of fluids with nanoparticles. In *Proceedings of 1995 International Mechanical Engineering Congress and Exhibition*, Vol. 66 (ASME, San Francisco, 1995).

- Aklu, S. et al. A review of thermophysical properties of water based composite nanofluids. *Renew. Sustain. Energy Rev.* **66**, 654–678 (2016).
- Gupta, M. et al. A review on thermophysical properties of nanofluids and heat transfer applications. *Renew. Sustain. Energy Rev.* **74**, 638–670 (2017).
- Tawfik, M. M. Experimental studies of nanofluid thermal conductivity enhancement and applications: a review. *Renew. Sustain. Energy Rev.* **75**, 1239–1253 (2017).
- Goodarzi, M. et al. Investigation of heat transfer performance and friction factor of a counter-flow double-pipe heat exchanger using nitrogen-doped, graphene-based nanofluids. *Int. Commun. Heat. Mass Transf.* **76**, 16–23 (2016).
- Eshgarf, H. & Afrand, M. An experimental study on rheological behavior of non-newtonian hybrid nano-coolant for application in cooling and heating systems. *Exp. Therm. Fluid Sci.* **76**, 221–227 (2016).
- Ray, D. R. & Das, D. K. Superior performance of nanofluids in an automotive radiator. *J. Therm. Sci. Eng. Appl.* **6**, 041002 (2014).
- Philipp, J., Shima, P. D. & Raj, B. Nanofluid with tunable thermal properties. *Appl. Phys. Lett.* **92**, 043108 (2008).
- Rasheed, A. K. et al. Heat transfer and tribological performance of graphene nanolubricant in an internal combustion engine. *Tribology Int.* **103**, 504–515 (2016).
- Branson, B. T. et al. Nanodiamond nanofluids for enhanced thermal conductivity. *ACS Nano* **7**, 3183–3189 (2013).
- Lamhot, Y. et al. Optical control of thermocapillary effects in complex nanofluids. *Phys. Rev. Lett.* **103**, 264503 (2009).
- Ciraulo, B. et al. Long-range optofluidic control with plasmon heating. *Nat. Commun.* **12**, 2001 (2021).
- Taylor, R. A., Otanicar, T. & Rosengarten, G. Nanofluid-based optical filter optimization for PV/T systems. *Light: Sci. Appl.* **1**, e34 (2012).
- Huang, G., Wang, K. & Markides, C. N. Efficiency limits of concentrating spectral-splitting hybrid photovoltaic-thermal (PV-T) solar collectors and systems. *Light: Sci. Appl.* **10**, 28 (2021).
- Estellé, P. et al. Current trends in surface tension and wetting behavior of nanofluids. *Renew. Sustain. Energy Rev.* **94**, 931–944 (2018).
- Richard, R. G. & Shankland, I. R. A transient hot-wire method for measuring the thermal conductivity of gases and liquids. *Int. J. Thermophys.* **10**, 673–686 (1989).
- Vladkov, M. & Barrat, J. L. Modeling transient absorption and thermal conductivity in a simple nanofluid. *Nano Lett.* **6**, 1224–1228 (2006).
- Yang, L. et al. A new thermal conductivity model for nanorod-based nanofluids. *Appl. Therm. Eng.* **114**, 287–299 (2017).
- Prasher, R., Bhattacharya, P. & Phelan, P. E. Thermal conductivity of nanoscale colloidal solutions (nanofluids). *Phys. Rev. Lett.* **94**, 025901 (2005).
- Verma, G. et al. Contactless thin-film rheology unveiled by laser-induced nanoscale interface dynamics. *Soft Matter* **16**, 7904–7915 (2020).
- Bezuglyi, B. A. & Chemozanov, S. I. Effect of delay of the thermocapillary response of a transparent liquid layer during laser heating of the absorbing substrate. *Tech. Phys.* **50**, 1243–1245 (2005).
- Da Costa, G. & Escalona, R. Time evolution of the caustics of a laser heated liquid film. *Appl. Opt.* **29**, 1023–1033 (1990).
- Zykov, A. Y. & Ivanova, N. A. Laser-induced thermocapillary convection in thin liquid layers: effect of thermal conductivity of substrates. *Appl. Phys. B* **123**, 235 (2017).
- Bezuglyi, B. A., Chemozanov, S. I. & Tarasov, O. A. New approach to diagnostics of organic impurities in water. *Colloids Surf. A: Physicochemical Eng. Asp.* **239**, 11–17 (2004).
- Won, J., Lee, W. & Song, S. Estimation of the thermocapillary force and its applications to precise droplet control on a microfluidic chip. *Sci. Rep.* **7**, 3062 (2017).
- Siposan, D. G. & Lukacs, A. Effect of low-level laser radiation on some rheological factors in human blood: an in vitro study. *J. Clin. Laser Med. Surg.* **18**, 185–195 (2000).
- Verma, G. & Singh, K. P. Time-resolved interference unveils nanoscale surface dynamics in evaporating sessile droplet. *Appl. Phys. Lett.* **104**, 244106 (2014).
- Verma, G. & Singh, K. P. Universal long-range nanometric bending of water by light. *Phys. Rev. Lett.* **115**, 143902 (2015).
- Verma, G., Pandey, M. & Singh, K. P. Interferometric technique for nanoscale dynamics of fluid drops on arbitrary substrates. *J. Appl. Phys.* **118**, 035306 (2015).
- Verma, G., Chaudhary, K. & Singh, K. P. Nanomechanical effects of light unveil photons momentum in medium. *Sci. Rep.* **7**, 42554 (2017).

31. Schroll, R. D. et al. Liquid transport due to light scattering. *Phys. Rev. Lett.* **98**, 133601 (2007).
32. Wunenburger, R. et al. Fluid flows driven by light scattering. *J. Fluid Mech.* **666**, 273–307 (2011).
33. Chaudhary, K. & Singh, K. P. Picometer resolved nanoscale optomechanics of micro-droplet. *Appl. Phys. Lett.* **115**, 251103 (2019).
34. Wedershoven, H. M. J. M. et al. Infrared laser induced rupture of thin liquid films on stationary substrates. *Appl. Phys. Lett.* **104**, 054101 (2014).
35. Chraïbi, H. & Delville, J. P. Thermocapillary flows and interface deformations produced by localized laser heating in confined environment. *Phys. Fluids* **24**, 032102 (2012).
36. Li, D. D. et al. Thermophysical performances of Al₂O₃-water nanofluids and its heat transfer enhancement in heat pipe. *Mater. Sci. Forum* **688**, 339–343 (2011).
37. Gao, Y. G. et al. Thermal conductivity and stability of novel aqueous graphene oxide–Al₂O₃ hybrid nanofluids for cold energy storage. *Appl. Sci.* **10**, 5768 (2020).
38. Gittings, S. et al. Characterisation of human saliva as a platform for oral dissolution medium development. *Eur. J. Pharmaceutics Biopharmaceutics* **91**, 16–24 (2015).
39. Jiang, Y. N. & Xu, Z. L. Numerical investigation of nanofluid thermocapillary convection based on two-phase mixture model. *Microgravity Sci. Technol.* **29**, 365–370 (2017).
40. Lu, G., Duan, Y. Y. & Wang, X. D. Surface tension, viscosity, and rheology of water-based nanofluids: a microscopic interpretation on the molecular level. *J. Nanopart. Res.* **16**, 2564 (2014).
41. Chinnam, J. et al. Measurements of the surface tension of nanofluids and development of a new correlation. *Int. J. Therm. Sci.* **98**, 68–80 (2015).
42. Richardson, H. H. et al. Experimental and theoretical studies of light-to-heat conversion and collective heating effects in metal nanoparticle solutions. *Nano Lett.* **9**, 1139–1146 (2009).
43. Oh, J. et al. The apparent surface free energy of rare earth oxides is governed by hydrocarbon adsorption. *Iscience* **25**, 103691 (2022).
44. Yan, X. et al. Atmosphere-mediated scalable and durable biphilicity on rationally designed structured surfaces. *Adv. Mater. Interfaces* **7**, 2000475 (2020).
45. Yan, X. et al. Atmosphere-mediated superhydrophobicity of rationally designed micro/nanostructured surfaces. *ACS Nano* **13**, 4160–4173 (2019).
46. Preston, D. J. et al. Effect of hydrocarbon adsorption on the wettability of rare earth oxide ceramics. *Appl. Phys. Lett.* **105**, 011601 (2014).
47. Cha, H. et al. Nanoscale-agglomerate-mediated heterogeneous nucleation. *Nano Lett.* **17**, 7544–7551 (2017).
48. Lukaszewicz, G. V. B. et al. A theoretical and experimental study of time-resolved thermal mirror with non-absorbing heat-coupling fluids. *Appl. Spectrosc.* **66**, 1461–1467 (2012).
49. Vajjha, R. S. & Das, D. K. Measurements of specific heat and density of Al₂O₃ nanofluid. *AIP Conf. Proc.* **1063**, 361–370 (2008).
50. Shah, J. et al. Temperature-dependent thermal conductivity and viscosity of synthesized α -alumina nanofluids. *Appl. Nanosci.* **7**, 803–813 (2017).
51. Dietzel, M. & Poulikakos, D. Laser-induced motion in nanoparticle suspension droplets on a surface. *Phys. Fluids* **17**, 102106 (2005).
52. Verma, G. & Yadav, G. Compact picometer-scale interferometer using twisted light. *Opt. Lett.* **44**, 3594–3597 (2019).
53. Stoev, I. D. et al. Highly sensitive force measurements in an optically generated, harmonic hydrodynamic trap. *eLight* **1**, 7 (2021).
54. Clark, J. L. & Rumbles, G. Laser cooling in the condensed phase by frequency up-conversion. *Phys. Rev. Lett.* **76**, 2037–2040 (1996).
55. Schmidt, M. A. et al. Hybrid nanoparticle–microcavity-based plasmonic nanosensors with improved detection resolution and extended remote-sensing ability. *Nat. Commun.* **3**, 1108 (2012).
56. Rodrigo, J. A., Angulo, M. & Alieva, T. Tailored optical propulsion forces for controlled transport of resonant gold nanoparticles and associated thermal convective fluid flows. *Light: Sci. Appl.* **9**, 181 (2020).